



Magnesium Elektron

SERVICE & INNOVATION IN MAGNESIUM



Magnesium Elektron UK,
P.O. Box 23, Rake Lane, Swinton, Manchester, M27 8DD, England.
Tel: 0161 911 1000 Fax: 0161 911 1010
Web: www.magnesium-elektron.com VAT No: GB 668 2142 26

A Division of MAGNESIUM ELEKTRON LIMITED. Registered in England No. 3141950.
Registered Office: The Victoria, 150-182 Harbour City, Salford Quays, Salford, M50 3SP
A Luxfer Group Company

Elektron 21

ELEKTRON 21 is a new high strength fully heat treatable magnesium based casting alloy for use at temperatures up to 400°F. This alloy has excellent corrosion resistance characteristics and castability.

APPLICATIONS

Magnesium Elektron has developed this lightweight, high performance alloy for motorsport and aerospace applications. It is designed to provide superior mechanical properties and improved corrosion resistance together with good castability.

SPECIFICATIONS

AMS 4429
UNS M12310

CHEMICAL COMPOSITION

Zinc	0.2 – 0.5%
Neodymium	2.6 – 3.1%
Gadolinium	1.0 – 1.7%
Zirconium	Saturated
Magnesium	Balance

HEAT TREATMENT

Castings are given the following T6 heat treatment to obtain optimum mechanical properties.

Solution treat for 8 hours at 520°C (970°F),

Hot water quench using water at 60 - 80°C (140-175°F) or polymer quench,

Age for 16 hours at 200°C (400°F),
Air cool.

PHYSICAL PROPERTIES

Specific gravity	1.82
Coefficient of thermal expansion	14.8 x 10 ⁻⁶ /°F
Thermal conductivity	67 Btu/ft h °F
Specific heat	0.24 Btu/lb °F
Electrical resistivity	94.6 nΩm
Modulus of elasticity	6.4 x 10 ³ ksi
Poissons ratio	0.27
Melting range	1013°F - 1184°F
Brinell hardness	65 - 75

DESIGN DATA

Minimum specification tensile properties.

0.2% Proof stress	21.0 ksi
Tensile strength	36.0 ksi
Elongation	2%

OTHER PROPERTIES

CASTABILITY

Excellent castability as a consequence of low oxidation characteristics.
Fine-grained microstructure.
Pressure tight.

PATTERN MAKERS SHRINKAGE FACTOR

1.5%

WELDABILITY

Weldable by the tungsten arc inert gas process (TIG) with a filler rod of a similar composition.
Castings should be heat treated after welding to obtain optimum properties.

MACHINING

ELEKTRON 21 castings, like all magnesium alloy castings, machine faster than any other metal. Providing the geometry of the part allows, the limiting factor is the power and speed of the machine rather than the quality of the tool material. The power required per cubic centimetre of metal removed varies from 9 to 14 watts per minute depending on the operation.

SURFACE TREATMENT

All the normal chromating, anodising and finishing treatments are applicable.

CORROSION RESISTANCE

ASTM B117 Salt spray test
Corrosion rate for base metal:
0.13 - 0.37mg/cm²/day
10 - 30 mpy

Elektron 21

AMBIENT TEMPERATURE MECHANICAL PROPERTIES

TYPICAL TENSILE PROPERTIES

0.2% Proof stress	24.7 ksi
Tensile strength	40.6 ksi
Elongation	5%

TYPICAL COMPRESSIVE PROPERTIES

0.2% Proof stress	24.4 ksi
Ultimate strength	53.2 ksi

TYPICAL SHEAR PROPERTIES

Ultimate stress	25 ksi
-----------------	--------

FRACTURE TOUGHNESS

K_{IC}	13.6 ksi inch ^{1/2}
----------	------------------------------

FATIGUE PROPERTIES

Pull-pull fatigue: R = 0.1	5 x 10 ⁷ cycles
	16.7-17.4 ksi

LOW TEMPERATURE MECHANICAL PROPERTIES


TYPICAL MECHANICAL PROPERTIES AT -31°F

Elongation:	7%
Ultimate tensile strength	39.2 ksi
Impact value(notched)	1.7J

ELEVATED TEMPERATURE MECHANICAL PROPERTIES


TYPICAL TENSILE PROPERTIES

FIG. 1 Effect of temperature on tensile properties

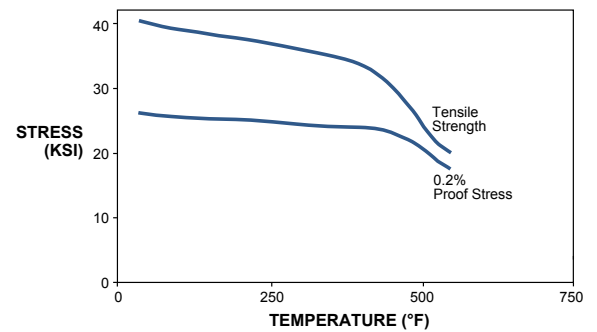

CREEP PROPERTIES

FIG. 2 Stress/time relationship at 400°F (0.1% creep strain)

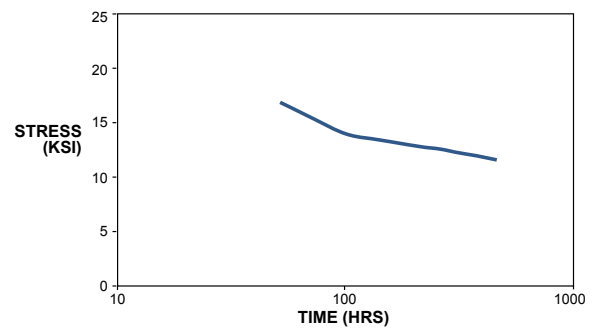

Certificate No. FM12677