



## ELEKTRON® ZK60A FORGINGS

### ZK60A

ZK60A is a wrought magnesium base alloy containing zinc and zirconium. Increased strength is obtained by artificial aging from the as-fabricated form. ZK60A-T5 has the best combination of strength and ductility at room-temperature of the wrought magnesium alloys.

### APPLICATIONS

Forgings in ZK60A find application in high strength parts for use primarily where the service temperature is below 150°C.

ZK60A forgings can be used where pressure tightness or machinability are required. That parts are dimensionally stable during and after machining is also an important design consideration.

Forgings in ZK60A find application in high strength parts for satellites, helicopter gearboxes and rotor hubs, bicycle frames, roadwheels, missile frames and interstage fairings, brake housings and landing gear struts.

### SPECIFICATIONS

UNS No. M16600

AMS4362

ASTM B91

FEDERAL QQ-M-40

### CHEMICAL COMPOSITION

Zinc	4.8-6.2%
Zirconium	0.45% min
Magnesium	Balance

### HEAT TREATMENT

As-fabricated (F) forgings can be converted to the precipitation treated temper (T5) by heating to 150°C for 24 hours, followed by air cooling.

### PHYSICAL PROPERTIES

Specific Gravity	1.83
Coefficient of Thermal Expansion	$27.1 \times 10^{-6} \text{K}^{-1}$
Thermal Conductivity	$121 \text{ Wm}^{-1}\text{K}^{-1}$
Specific Heat	$1100 \text{ Jkg}^{-1}\text{K}^{-1}$
Electrical Resistivity	57 nΩm
Modulus of Elasticity	45GPa
Poissons Ratio	0.35
Melting Range	520-635°C

### DESIGN DATA

Specification minimum tensile properties.

#### ZK60A-T5 Die Forgings

0.2% Proof Stress	180 MPa
Tensile Strength	290 MPa
Elongation in 5.65√A	6%

#### ZK60A-T6 Die Forgings

0.2% Proof Stress	220 MPa
Tensile Strength	295 MPa
Elongation in 5.65√A	3%

## OTHER PROPERTIES

---

### TYPICAL HARDNESS

---

ZK60A-T6	85 Rockwell E
ZK60A-T5	77 Rockwell E

### WELDABILITY

---

ZK60A is not considered to be weldable by conventional techniques due to hot-shortness cracking. However, resistance welding response is excellent. Friction stir welding can be used to join ZK60A to itself and other magnesium alloys.

### MACHINING

---

ZK60A, like all magnesium alloy forgings, machines faster than any other metal. Providing the geometry of the part allows, the limiting factor is the power and speed of the machine rather than the quality of the tool material. The power required per cubic centimeter of metal removed varies from 9 to 14 watts per minute depending on the operation.

### SURFACE TREATMENT

---

All the normal chromating, anodizing, plating, and finishing treatments are readily applicable.

### CORROSION RESISTANCE

---

ASTM B117 Salt Spray Test	
Corrosion Rate	0.6 mg/cm <sup>2</sup> /day 50 mpy

## AMBIENT TEMPERATURE MECHANICAL PROPERTIES FOR T5 TEMPER

---

### TYPICAL TENSILE PROPERTIES

---

0.2% Proof Stress	200 MPa
Tensile Strength	310 MPa
Elongation in 5.65√A	13%

### TYPICAL COMPRESSIVE PROPERTIES

---

0.2% Proof Stress	160 MPa
-------------------	---------

### TYPICAL SHEAR PROPERTIES

---

Ultimate Stress	165 MPa
-----------------	---------

### TYPICAL BEARING PROPERTIES

---

0.2% Proof Stress	285 MPa
Ultimate Stress	420 MPa

### FRACTURE TOUGHNESS

---

K <sub>IC</sub>	34 MPa√m
-----------------	----------

### FATIGUE PROPERTIES

---

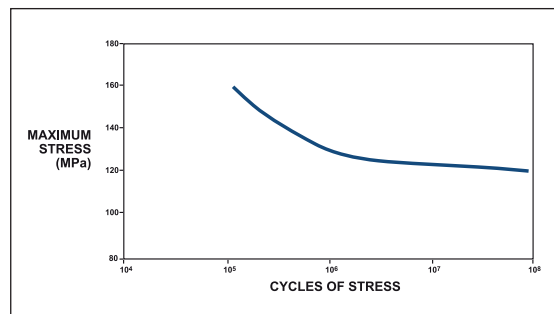


FIG. 1 Rotating bend fatigue test

# ELEKTRON<sup>®</sup> ZK60A FORGINGS

## ELEVATED TEMPERATURE MECHANICAL PROPERTIES FOR T5 TEMPER

### TYPICAL TENSILE PROPERTIES

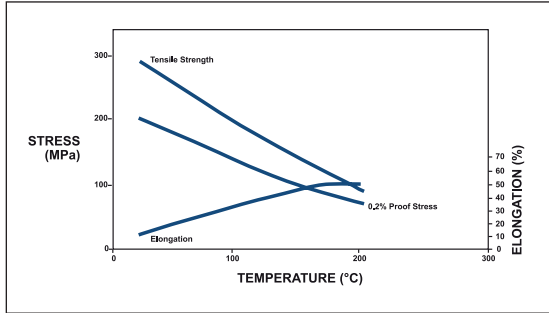


FIG. 2 Effect of temperature on tensile properties

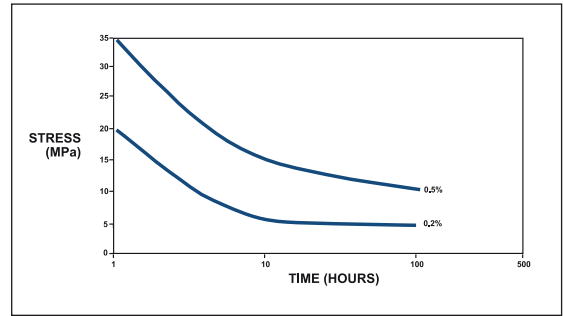


FIG. 4 Stress/time relationship for specified creep at 150°C

### CREEP PROPERTIES

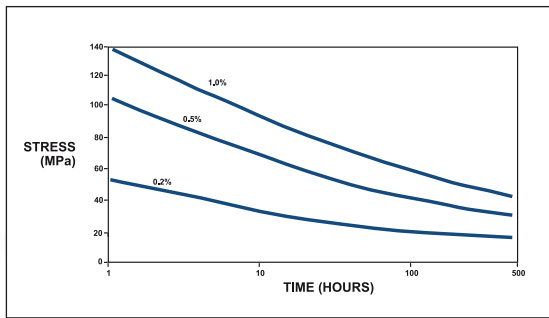


FIG. 3 Stress/time relationship for specified creep at 100°C

† The information contained within is meant as a guideline only

© Copyright Magnesium Elektron Ltd 2014. The information provided within this document is aimed to assist manufacturers and other interested parties in the use of magnesium alloys. Magnesium Elektron accepts no liability in whole or in part from use and interpretation of the data herein. All information is given in good faith but without warranty. Freedom from patent rights must not be assumed. Health and Safety information is available for all Magnesium Elektron products. MAGNESIUM ELEKTRON, THE 'e' LOGO, MEL, ELEKTRON and ZIRMAX are registered trademarks of Magnesium Elektron Limited.



Certificate No. FM12677